

Preparation and Characterization of Magnetite (Fe_3O_4) nanoparticles By Sol-Gel Method

Zakiyyu I. Takai^{1,2}, Mohd K. Mustafa^{1,2*}, Saliza Asman² and Khairunnadim A. Sekak^{3*}

¹Microelectronic and Nanotechnology-Shemsuddin Research Centre (Mint-SRC) Uvniversiti Tun Hussein Onn Malaysia (UTHM).

²Department of Physics and Chemistry, Faculty of Applied Sciences and Technology, Universiti Tun Hussein Onn Malaysia, Educational Hub Pagoh, 84000, Muar, Johor, Malaysia.

³ Faculty of Applied Sciences, Universiti Teknologi Mara. 40450 Shah Alam, Salangor, Malaysia.

Received 18 March 2018; Revised 12 July 2018; Accepted 29 July 2018

ABSTRACT

The magnetite (Fe_3O_4) nanoparticles were successfully synthesized and annealed under vacuum at different temperature. The Fe_3O_4 nanoparticles prepared via sol-gel assisted method and annealed at 200-400°C were characterized by Fourier Transformation Infrared Spectroscopy (FTIR), X-ray Diffraction spectra (XRD), Field Emission Scanning Electron Microscope (FESEM) and Atomic Force Microscopy (AFM). The XRD result indicate the presence of Fe_3O_4 nanoparticles, and the Scherer's Formula calculated the mean particles size in range of 2-25 nm. The FESEM result shows that the morphologies of the particles annealed at 400°C are more spherical and partially agglomerated, while the EDS result indicates the presence of Fe_3O_4 by showing Fe-O group of elements. AFM analyzed the 3D and roughness of the sample; the Fe_3O_4 nanoparticles have a minimum diameter of 79.04 nm, which is in agreement with FESEM result. In many cases, the synthesis of Fe_3O_4 nanoparticles using FeCl_3 and FeCl_2 has not been achieved, according to some literatures, but this research was able to obtained Fe_3O_4 nanoparticles base on the characterization results.

Keyword: Sol-Gel Method, Magnetite Nanoparticles, Particles Size, Morphologies, XRD.

1. INTRODUCTION

Recently, the magnetite (Fe_3O_4) nanoparticles have been explored extensively due to their unlimited physical and chemical properties at the nanoscale [1]. In most of the application of magnetite nanoparticles, uniform shape and size particles are required to be well dispersed in the solvent. The major factors that influence the interest of many researchers are the particles size. However, the shape and size of the Fe_3O_4 nanoparticles usually controlled by their synthesis techniques. Therefore, synthesis technique is the most significant method for preparation of certain materials, such as metal oxide powder and ceramic materials [2]. Magnetite nanoparticles synthesized with effective properties such as shape, size and suitable morphologies, will help to achieve a wider range of application [3]. Up to now, the focus have been made on the synthesis of iron oxide particles because it can be crystalline in different polymorphic phases which include hematite ($\alpha\text{-Fe}_2\text{O}_3$), maghemite ($\gamma\text{-Fe}_2\text{O}_3$), and magnetite (Fe_3O_4) [4]. Among these inorganic nanoparticles, Fe_3O_4 nanoparticles has interesting electric and magnetic properties as well as extensive potential applications in colour imaging, magnetic recording media, soft magnetic materials, ferrofluid, spintronic and biomedical applications such as drugs delivery, cell separation, imaging and therapeutic in vivo technology [3,4].

* Corresponding Author: zitakai21@gmail.com

Numerous synthesis method like co-precipitation method [5], hydrothermal method [6], microwave irradiation method [7], ultrasonic method [8] and sol-gel method [9] have been used to synthesize magnetite nanoparticles.

Among all synthesis method, sol-gel techniques has been chosen compared to the remaining traditional synthesis techniques due to its advantageous properties including low cost, high purity, and suitable homogeneity [10]. However, in the quest to produce nanoparticles by sol-gel techniques suitable for product, many parameter need to be optimized to control the reaction condition [11,12]. It was gathered that, increasing the reactivity enhance wider surface area of the nanoparticles obtained by sol-gel techniques [13]. In recent time, the attention have been on the preparation of magnetite nanoparticles in order to overcome certain problem, through different chemical synthesis method, although a lot of research have been published demonstrating the preparation of magnetite (Fe_3O_4) nanoparticles using several method for different applications such as drug delivery, magnetic recorder, ferrofluid and sensing application [14, 15]. Furthermore, the Fe_3O_4 nanoparticles were prepared by [16, 17] through sol-gel method using cheapest materials of ferric nitrate as the precursor. The Fe_3O_4 nanoparticles was observed at 250°C . When the temperature rises to 350°C , the hematite (Fe_2O_3) also appear causing major deficiency that hinder its applications [18-20]. In the research reported by [21-23], sol-gel method were used to synthesized iron oxide and its mixture using ethylene glycol, FeCl_3 and FeCl_2 , but the magnetite nanoparticles has not been observed.

In this work, the Fe_3O_4 nanoparticles were prepared effectively through sol-gel techniques and it was annealed under vacuum in different temperature. The major material used in the synthesis of Fe_3O_4 nanoparticles are iron (III) chloride (FeCl_3), iron (II) chloride (FeCl_2) and ethylene glycol ($\text{C}_2\text{H}_6\text{O}$). The Fe_3O_4 nanoparticles samples are prepared in the form of S1, S2 and S3 with different annealed temperature of 200°C , 300°C and 400°C respectively. The morphologies of the Fe_3O_4 nanoparticles annealed at 400°C were found to be more spherical and partially agglomerated with continues size distribution.

2. EXPERIMENTAL METHOD

2.1 Materials

Iron (III) chloride $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$, Iron (II) chloride $\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$ and ethylene glycol ($\text{C}_2\text{H}_6\text{O}$) grade were obtained from SIGMA ALDRICH chemical cooperation. The entire reagents were used without any further purification.

2.2 Synthesis of Fe_3O_4 Nanoparticles

The synthesis of magnetite nanoparticles is described as follows: 2.35g of Fe (III) and 8.35g of Fe (II) were firstly dissolved in 60 ml of ethylene glycol and vigorously stirred for a period of 3h at 45°C to form a sol. Subsequently, the sol was heated and maintained at a temperature of 80°C until dark colour gel was formed. This gel was aged for a period of 72h and later dried at 140°C for 5h. The obtained xerogel was annealed at a certain temperature ranging from 200 - 400°C under vacuum condition. Finally, different size magnetite nanoparticles were successfully obtained. The synthesized Fe_3O_4 nanoparticles were washed with a certain amount of acetone and ethanol several times to enhance its magnetic properties. Table 1 tabulates the effect of a change in temperature towards the mean size of magnetic nanoparticles calculated from XRD data using Scherrer's formula (see Figure 4). However, from Table 1, the Fe_3O_4 nanoparticles size increases as the annealing temperature increases.

Table 1 Effect of change in temperature toward the mean size of magnetite nanoparticles

Sample	Annealing temperature (°C)	Mean particles size (nm)
S1	200	2.02
S2	300	5.58
S3	400	8.35

2.3 Characterization

A sample was characterized using the Fourier Transform Infrared Spectrum (FTIR) (Perkin Elmer Spectrum 100 FTIR spectrometer). The absorption spectra of the magnetite nanoparticles were determined using Ultraviolet (Uv-Vis) spectroscopy (SHIMDZU 1800 UV-visible series). The X-ray diffraction spectroscopy (XRD) (Shimadzu XD-610) is used to determine the phase structure of the magnetite nanoparticles; the rays were radiated at a wavelength of ($\lambda = 0.15406$ nm). However, the morphological analysis of the particles were obtained by Field Emission Scanning Electron Microscope (FESEM JEOL model JDM-7600F) equipped with X-ray dispersive spectrometer (EDS). To quantitatively examined the high and three dimension (3D) profiles of the structure formed by Fe_3O_4 , Atomic Force Microscopes (AFM) (Bruker 59×413) was used in the tapping mode to image the topography of a two-layer grid formed by Fe_3O_4 . The 3D image showed the spatial profiles of the grids.

3. RESULT AND DISCUSSION

3.1 Fourier Transform Infrared Spectra (FTIR) Analysis

The analysis of the infrared (IR) spectra confirms the monomer fixation of Fe_3O_4 nanoparticles (Figure 1), which resulted in the formation of Fe-O bands which is proven by the appearance of the absorptions band at 476cm^{-1} , 519cm^{-1} , 688cm^{-1} , 743cm^{-1} and 875cm^{-1} [7-10]. Moreover, the existence of peaks at 1069cm^{-1} to 1600cm^{-1} and 2606cm^{-1} to 2941cm^{-1} are assigned to O-H stretching, C-H stretching, C=C stretching, C=O stretching and C-O stretching bands respectively, indicating acidic medium condition of Fe_3O_4 nanoparticles preparation [19, 23]. The bonds appear at 3226cm^{-1} , 3293cm^{-1} and 3325cm^{-1} may be attributed to the H_2O molecules or O-H vibrating stretching which are probably existed due to ethylene glycol $(\text{CH}_2\text{OH})_2$ [24].

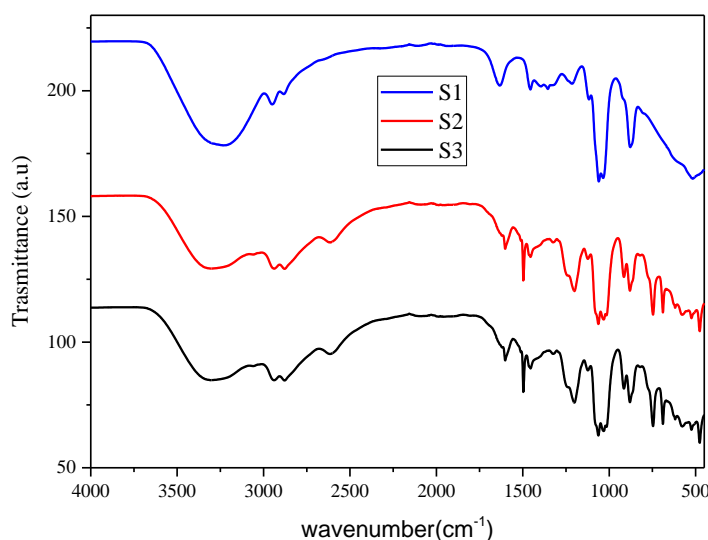


Figure 1. FTIR spectra of the magnetite nanoparticles.

3.2 UV-Visible Spectroscopy Study

The UV-visible spectroscopy was used to characterize the structure of Fe₃O₄ nanoparticles. Figure 2 reveals that the absorption peaks of the prepared Fe₃O₄ nanoparticles was found within the average UV-vis absorption region [5, 17], the average lower absorption wavelength of 262.13nm and 230 nm is observed in all the samples. This can easily be assigned to the intrinsic band gap absorption of the magnetite nanoparticles. The mobility of electrons from valence band to conduction band can be determined by the equation of the energy gap (E_g) of the Fe₃O₄ nanoparticles, was calculated using the relation

$$E_g = \frac{hc}{\lambda} \quad (1)$$

Where c is the velocity of light, h is the Planck constant, λ is the wavelength of light the estimated band gap energy result is 4.7.eV

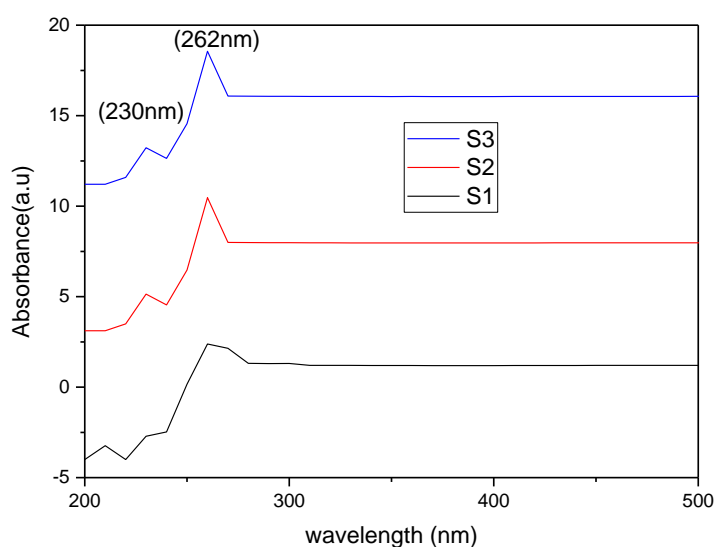


Figure 2. UV-visible spectra of the magnetite nanoparticles.

3.2 The Analysis Pattern of XRD in Magnetite (Fe₃O₄) Nanoparticles

The X-ray diffraction (XRD) pattern of the Fe₃O₄ nanoparticles was obtained at different annealing temperatures as shown at diffraction peak of $2\theta = 26.75^\circ$, 32.67° , 35.44° , 55.88° , and 62.55° . This can be assigned to (310), (110), (311), (440), and (330) crystal planes of pure Fe₃O₄ nanoparticles with spinal structure of (JCPDS98-3969) [7, 21], respectively in 200°C and 300°C. At 400°C some peaks are also observed at 46.54° and 55.98° which can be easily be assigned to (331), and (240). This indicates that these peaks are related to γ -Fe₂O₃ of (JCPDS98-0625) and α -Fe₂O₃ of (JCPDS98-2012) [22, 23] respectively, these data are in agreement with what was reported by [16, 18]. This reveals that the resultants nanoparticles in the first sample (S1) is purely Fe₃O₄ nanoparticles [25], while the remaining second (S2) and third (S3) samples are probably γ -Fe₂O₃ and α -Fe₂O₃ nanoparticles, respectively [26]. The peak of the sample S1 in Figure 3 matched very well with Fe₃O₄ of (JCPDS98-3969) nanoparticles, same peaks are shifted slightly to the higher angle in the S2, which is possibly due to oxidation of Fe₃O₄ in air at 300°C resulted to γ -Fe₂O₃ same result of this transformation of Fe₃O₄ to γ -Fe₂O₃ have been reported in the literature by [13, 25]. The XRD pattern of the S3 indicates the oxidation of Fe₃O₄ at 400°C in air. The diffraction peaks matched well with α -Fe₂O₃ (JCPDS98-2012), showing the transformation of Fe₃O₄ to α -Fe₂O₃ at 400°C in air [8, 11].

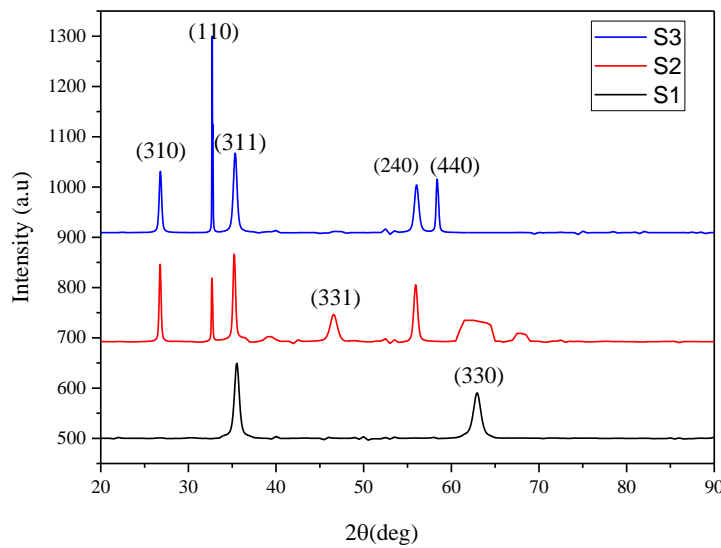


Figure 3. XRD analysis of Fe₃O₄ nanoparticles obtained at different temperature.

The following is the Scherer's formula used to calculated the crystalline particles size:

$$D = \frac{K \cdot \lambda}{\beta \cdot \cos \theta} \quad (2)$$

Where K (0.94) is a dimensionless quantity, λ is the X-ray wavelength, β is the line broadening at half-maximum intensity (FWHM) and θ is the Bragg angle. Therefore, the obtained particles size result is plotted as the function of temperature in (Figure 5). As observed in the plot, the magnetite nanoparticles size increase as the temperature increases from 200°C to 400°C. Therefore, the average particles size as calculated by Scherer's formula is 2.02nm, 5.58nm and 8.35nm for S1, S2, and S3 respectively. This shows that, with rising annealing temperatures, the size of the Fe₃O₄ nanoparticles is gradually increasing as shown.

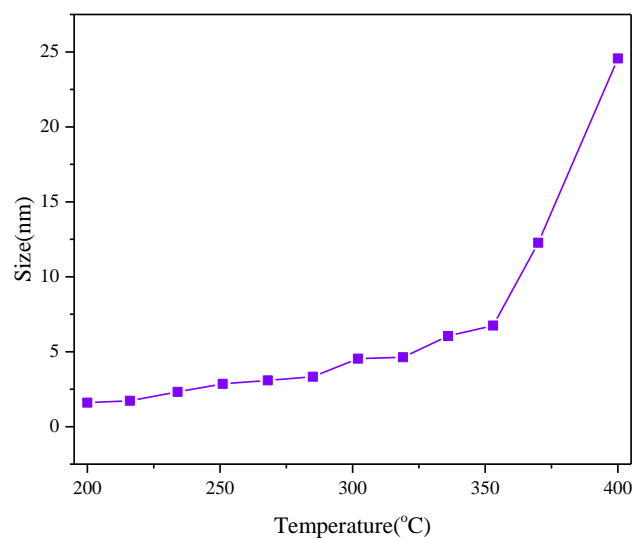


Figure 4. Size of Fe₃O₄ nanoparticles calculated using Scherer's formula as a function of annealing temperature.

3.3 Field Emission Scanning Electron Microscope (FESEM) and Energy Dispersive Spectrometer (EDS) Image of Magnetite (Fe_3O_4) Nanoparticles

FESEM observed the morphologies of the (Fe_3O_4) nanoparticles; the obtained images are shown in (Figure 5). The Fe_3O_4 nanoparticles sample (S3) annealed at 400°C appeared in a spherical structure and nearly agglomerated. However, the spherical nanoparticles exhibit magnificent internationalisation rate and highest cellular take up instead of another shape such as nanorods, nanocubes or nanodisk [25]. Moreover, due to strong inter-particles Van der Waals force and magnetic attraction among the Fe_3O_4 nanoparticles, some agglomeration is detected in the samples (S3). The irregular shapes are observed at elevated changes in temperature (see S1 and S2) due to agglomeration process [22, 23]. The image obtained through EDS analysis shown in (Figure 5) confirmed the appearance of Fe_3O_4 nanoparticles by indicating Fe-O group of the element.

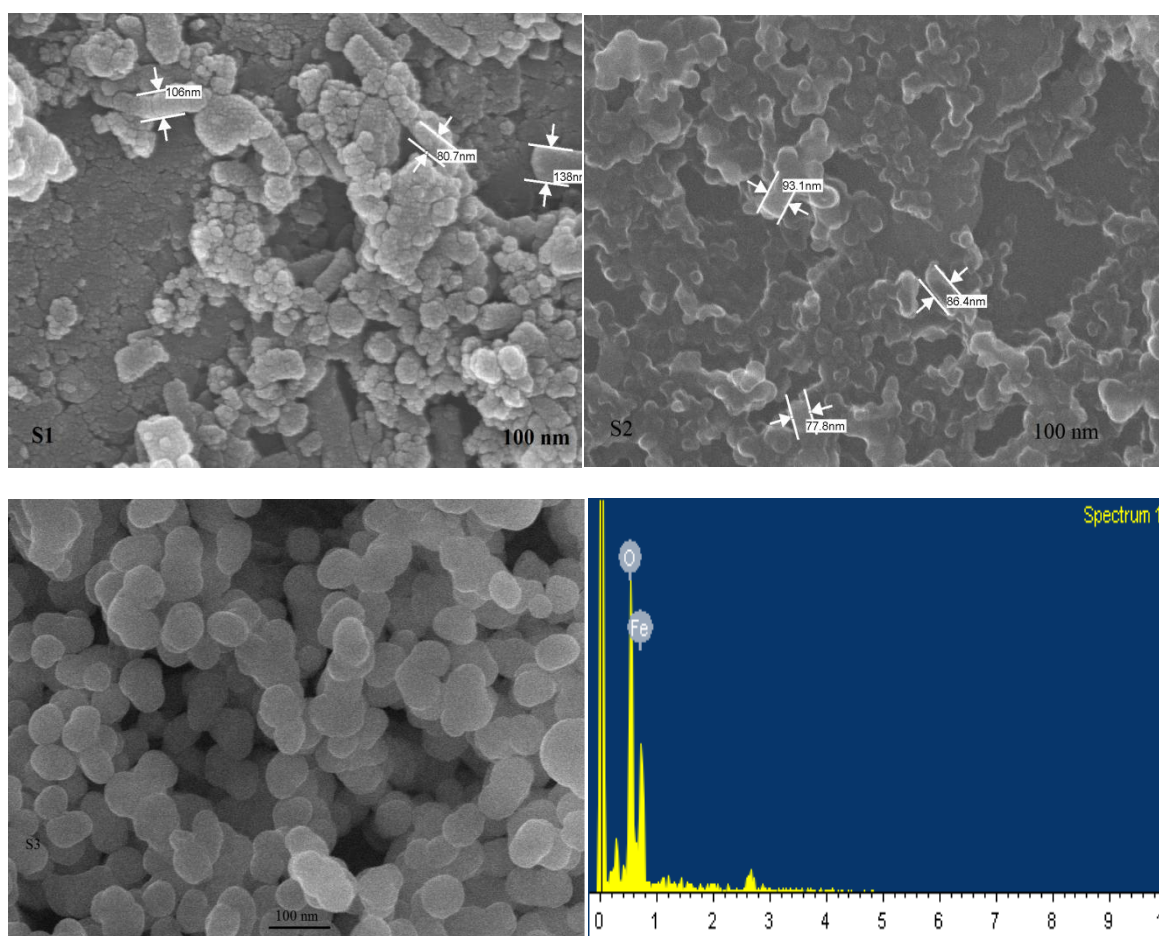


Figure 5. FESEM image of magnetite nanoparticles annealed under vacuum at 200°C for S1, 300°C for S2 and 400°C for S3 and the EDS image of magnetite (Fe_3O_4) nanoparticles.

3.4 Atomic Force Microscope (AFM) Characterization

The magnetite nanoparticles were deposited and dried on the glass for AFM characterization. The results were obtained to determine the three dimensions (3D) and roughness of the samples. Figure 5 shows the resulting 3D images of the sample, the maximum high of the particles is about 10.4nm and the diameter of 79.09nm for the scanned area of $1\mu\text{m} \times 1\mu\text{m}$ according to histogram in Figure 6. This result is in agreement with particles size obtained by FESEM. The knobs spots (yellow spots) indicate the present of small agglomeration of Fe_3O_4

nanoparticles, which is also seen as a yellow area at phase contrast of the 3D image as reported by [23]. The light yellow area is obtained due to the high moisture content in the ethylene glycol; the sample was melted down because of heat absorption from the laser light [26-28].

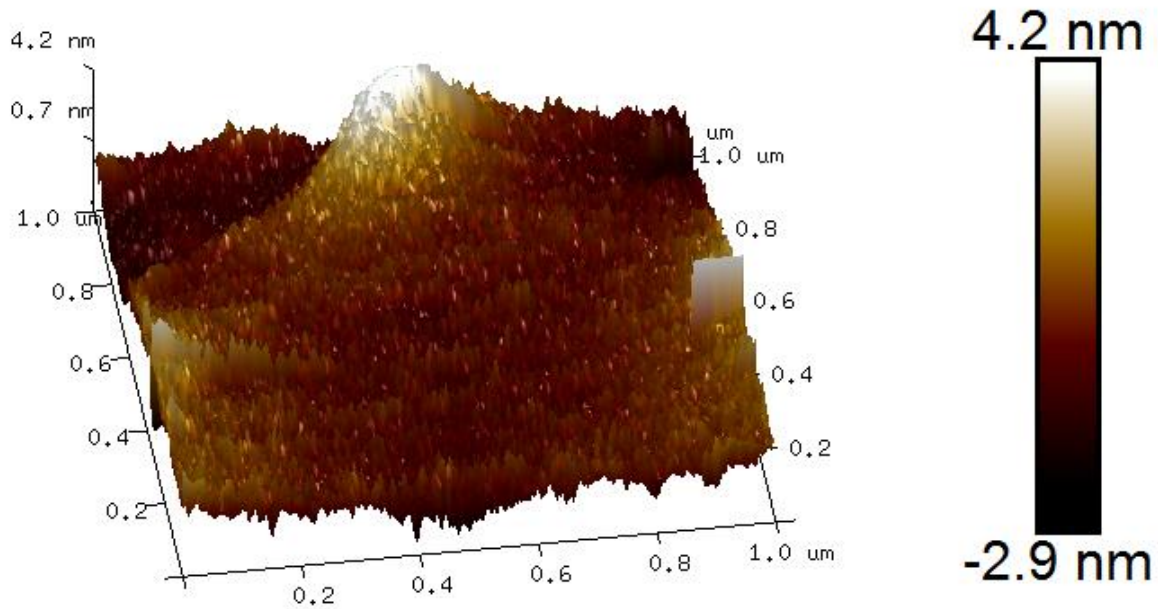


Figure 5. AFM 3D image of the magnetite nanoparticles annealed at 400°C.

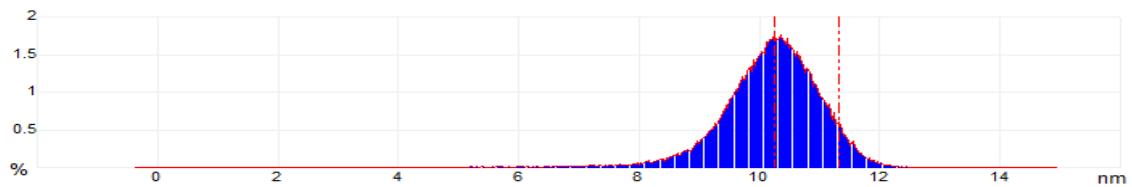


Figure 6. Histogram obtained from AFM Analysis.

4. CONCLUSION

This research has demonstrated the preparation of Fe_3O_4 nanoparticles by sol-gel assisted method and annealed under vacuum at different temperature 200-400°C. The phase and molecular structure, functional group, morphologies and roughness analysis of the Fe_3O_4 nanoparticles were successfully characterized; the results indicated that the different sized Fe_3O_4 nanoparticles were obtained, simply by varying annealing temperature. The morphologies observed by FESEM shows that the sample S3 annealed at 400°C is more spherical and different size Fe_3O_4 nanoparticles were observed in S1, and S2 annealed at 200 and 300°C respectively. This method offers several significant properties for the preparation of Fe_3O_4 nanoparticles. Firstly, the synthetic method is economically important and environmentally friendly, because it includes cheaper and toxic free iron salts. Secondly, the size of the obtained Fe_3O_4 nanoparticles can be easily controlled by varying the annealing temperature.

ACKNOWLEDGEMENT

The authors gratefully acknowledge the Centre for Graduate Studies (CGS) Universiti Tun Hussein Onn Malaysia (UTHM) and Universiti Teknologi Mara (UiTM) for their kind support and encouragement through this research.

REFERENCES

- [1] H. Kavas, M. Günay, A. Baykal, M. S. Toprak, H. Sozeri & B. Aktaş, "Negative Permittivity of Polyaniline-Fe₃O₄ Nanocomposite," *J. Inorg. Organomet. Polym. Mater.*, **23**, 2 (2013) 306–314.
- [2] S. Chattopadhyay, O. P. Bajpai & D. K. Setua, "A Brief Overview on Ferrite (Fe₃O₄) Based Polymeric Nanocomposites: Recent Developments and Challenges," *J. Res. Updat. Polym. Sci.*, **3**, 4 (2015) 184–204.
- [3] O. M. Lemine, *et al.*, "Sol-gel synthesis of 8nm magnetite (Fe₃O₄) nanoparticles and their magnetic properties," *Superlattices Microstruct.*, (2012).
- [4] H. Cui, Y. Liu & W. Ren, "and low temperature sol – gel synthesis of nearly monodispersed iron oxide nanoparticles," *Adv. Powder Technol.*, **24**, 1 (2013) 93–97.
- [5] X. L. Wang, L. Wei, G. H. Tao & M. Q. Huang, "Synthesis and characterization of magnetic and luminescent Fe₃O₄/CdTe nanocomposites using aspartic acid as linker," *Chinese Chem. Lett.*, **22**, 2 (2011) 233–236.
- [6] B. Li, X. Weng, G. Wu, Y. Zhang, X. Lv & G. Gu, "Synthesis of Fe₃O₄/polypyrrole/polyaniline nanocomposites by in-situ method and their electromagnetic absorbing properties," *J. Saudi Chem. Soc.*, **21**, 4 (2017) 466–472.
- [7] A. H. M. Yusoff, M. N. Salimi, M. F. Jamlos & A. Yusoff, "Synthesis and characterization of biocompatible Fe₃O₄ nanoparticles at different pH Synthesis and Characterization of Biocompatible Fe₃O₄ Nanoparticles at Different pH," *AIP Conf. Proc.*, **1835** (2017) 20010–20004.
- [8] O. M. Lemine, *et al.*, "Sol-gel synthesis of 8nm magnetite (Fe₃O₄) nanoparticles and their magnetic properties," *Superlattices Microstruct.*, **52**, 4 (2012) 793–799.
- [9] M. Bhaumik, A. Maity & V. K. Gupta, "Synthesis and characterization of Fe₀ /TiO₂ nanocomposites for ultrasound assisted enhanced catalytic degradation of reactive black 5 in aqueous solutions," *J. Colloid Interface Sci.*, **506** (2017) 403–414.
- [10] M. Aghazadeh & F. Aghazadeh, "Improve Synthesis of Iron Oxide Nanorode with Hydrothermal Method," **74** (2013) 67–74.
- [11] J. B. Mamani, L. F. Gamarra & G. E. de S. Brito, "Synthesis and characterization of Fe₃O₄ nanoparticles with perspectives in biomedical applications," *Mater. Res.*, (2014).
- [12] X. Han & Y.-S. Wang, "Studies on the synthesis and microwave absorption properties of Fe₃O₄/polyaniline FGM," *Phys. Scr.*, **T129** (2007) 335–339.
- [13] J. Xu, *et al.*, "Preparation and magnetic properties of magnetite nanoparticles by sol-gel method," *J. Magn. Magn. Mater.*, (2007).
- [14] W. S. Chiu, S. Radiman, M. H. Abdullah, P. S. Khiew, N. M. Huang & R. Abd-Shukor, "One pot synthesis of monodisperse Fe₃O₄ nanocrystals by pyrolysis reaction of organometallic compound," *Mater. Chem. Phys.*, **106**, 2–3 (2007) 231–235.
- [15] J. B. Mamani, L. F. Gamarra & G. E. de S. Brito, "Synthesis and characterization of Fe₃O₄ nanoparticles with perspectives in biomedical applications," *Mater. Res.*, **17**, 3 (2014) 542–549.
- [16] Y. Yao, H. Jiang, J. Wu, D. Gu & L. Shen, "Synthesis of Fe₃O₄ /polyaniline nanocomposite in reversed micelle systems and its performance characteristics," *Procedia Eng.*, **27** (2011) 664–670.
- [17] N. J. Tang, W. Zhong, H. Y. Jiang, X. L. Wu, W. Liu & Y. W. Du, "Nanostructured magnetite (Fe₃O₄) thin films prepared by sol-gel method," *J. Magn. Magn. Mater.*, **282**, 1–3 (2004) 92–95.

- [18] Z. I. Taka, M. K. Mustafa, S. Asman, K. Ahmad, and S. Jibrin, "Preparation of Aniline Dimer-COOH Modified Magnetite (Fe_3O_4) Nanoparticles by Ultrasonic Dispersion Method," vol. **7**, (2018) pp 185–188.
- [19] Z. Jin, *et al.*, "Enhanced magnetic and electrochemical properties of one-step synthesized PANI- Fe_3O_4 composite nanomaterial by a novel green solvothermal method," *J. Alloys Compd.*, **695** (2017) 1807–1812.
- [20] H. N. Azlina, J. N. Hasnidawani, H. Norita & S. N. Surip, "Synthesis of SiO_2 Nanostructures Using Sol-Gel Method," *Acta Phys. Pol. A*, **129**, 4 (2016) 842–844.
- [21] S. Shafiee, O. Akhavan, H. Hatami & P. Hoseinkhani, "Sol-gel synthesis of thermoluminescent Cd-doped ZnTe nanoparticles," *Indian J. Pure Appl. Phys.*, **53**, 12 (2015) 804–807.
- [22] Z. I. Takai, M. K. Mustafa, and S. Asman, "Preparation of high performance conductive polyaniline magnetite (PANI/ Fe_3O_4) Nanocomposites by Sol-Gel Method," *Asian J. Chem.*, vol. **30**, no. 12, (2018) 2625-2630.
- [23] M. Bilton, S. J. Milne & A. P. Brown, "Comparison of Hydrothermal and Sol-Gel Synthesis of Nano-Particulate Hydroxyapatite by Characterisation at the Bulk and Particle Level," *Open J. Inorg. Non-metallic Mater.*, **2**, 1 (2012) 1–10.
- [24] M. Jamal, M. Z. Noh, S. Al-juboor, M. Haziman, B. Wan, and Z. Ibrahim, "Mechanical Properties of the Concrete Containing Porcelain Waste as Sand," vol. **7**, (2018) pp. 180–184.
- [25] M. Jamshidiyan, A. S. Shirani & G. Alahyarizadeh, "Solvothermal synthesis and characterization of magnetic Fe_3O_4 nanoparticle by different sodium salt sources," *Mater. Sci.*, **35**, 1 (2017) 50–57.
- [26] S. Shaker, S. Zafarian, C. S. Chakra & K. V. Rao, "preparation and characterization of magnetite nanoparticles by sol-gel method for water treatment," *Int. J. Innov. Res. Sci. Eng. Technol.*, **2**, 7 (2013).
- [27] M. Niederberger, "Nonaqueous Sol – Gel Routes to Metal Oxide Nanoparticles," *Acc. Chem. Res.*, **40**, 9 (2007) 793–800.
- [28] J. Mohammed *et al.*, "Tuning the dielectric and optical properties of Pr–Co–substituted calcium copper titanate for electronics applications," *J. Phys. Chem. Solids*, vol. 126, no. September **201**(8), pp. 85–92, 2019.

